

Growth-related inhomogeneities in bulk melt-grown YBaCuO crystals

A. B. Surzhenko*, S. Schauroth, D. Litzkendorf, M. Zeisberger, T. Habisreuther, and W. Gawalek
Institut für Physikalische Hochtechnologie, Winzerlaer Str. 10, D-07745 Jena, Germany

The homogeneity of a large $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (YBCO) sample fabricated by top-seeded melt-growth has been studied in details. It was particularly shown how structural imperfections and superconducting properties are distributed along the growth front. These distributions are scarcely explicable within a suggestion that the a-growth fronts are flat. The obtained data testify to concave growth fronts.

1. Introduction

The magnetic flux trapping ability of bulk high-temperature superconductors (HTS), which promises their wide usage as cryomagnets [1] operating at liquid nitrogen temperature $T_{LN} \approx 77\text{ K}$, depends on their critical current density j_c and the length scale d over which it flows [2]. Therefore, rather large sizes ($d \gg 1\text{ cm}$) are required for existing $\text{REBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (RE: Y, Sm, Eu, Nd, *etc.*) crystals with $j_c(T_{LN}) \approx 10^4\text{ A/cm}^2$ to trap the peak fields $\mu_0 H \geq 1\text{ T}$ and, consequently, to seem more attractive than conventional permanent magnets. However, so large distances, which the growth front has to cover from the seeding point, inevitably result in negative changes of growth conditions. That is why Dewhurst *et al.* observed a certain degradation of the crystal microstructure in the radial direction (from the crystal center towards the edges) and, because of a short coherence length ξ (e.g., $\xi_c \approx 0.3\text{ nm}$ and $\xi_{ab} \approx 2\text{ nm}$ in the $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (YBCO) material), that of superconducting properties [3]. Apart from the radial inhomogeneities the lateral ones were also recently revealed [4]. In particular, the lateral distribution of a flux trapped by the YBCO crystal after its magnetization by short magnetic pulses, was demonstrated to ensue from its growth in five growth sectors (GS), i.e. the sectors grown on different habit planes (see Fig. 1).

This paper reports the detailed study how superconducting properties of a large YBCO sample

vary along the a-habits, (100) and/or (010), and correlates these effects with the spatial distribution of the structure inhomogeneities, i.e. grain boundaries (GB), Y_2BaCuO_5 ('211') inclusions and oxygen deficient zones. The obtained data are hard to explain in terms of flat habitus planes, these testify to concave growth fronts.

2. Experimental results

The YBCO sample with a diameter of 30 mm and a thickness of 20 mm was fabricated from the mixture of commercially purchased powders (Solvay GmbH, Germany) with 1 wt.% CeO_2 by usual peritectic solidification, which details are

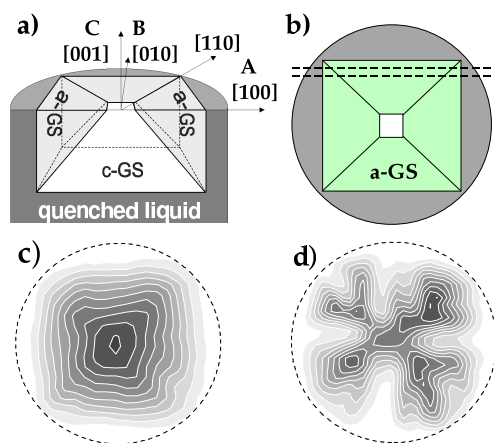


Figure 1. Schematic diagram (a), (b) for a typical bulk melt-grown YBCO sample. Compare nearly regular tetragonal shape of isolines on the remanent flux map obtained after a static FC-magnetization (c) to their X-like distribution [4] remaining after the magnetic pulse (d).

*Corresponding author. On leave from Institute for Magnetism, Kiev, Ukraine. E-mail: surzhenko@ipht-jena.de

given in Refs. [4,5], and post-annealed in oxygen atmosphere. The YBCO crystal appeared a large single grain (please, note nearly regular tetragonal shape of isolines on the remanent flux map, Fig. 1c) which grew as shown in Figs. 1(a),(b), i.e. in four a-GSs grown on the (100), (010), ($\bar{1}00$) and (0 $\bar{1}0$) habit planes and c-GS which habit, (001), is perpendicular to the cylinder axis [6].

A slice of width 2.8 mm (marked in Fig. 1(b) by dashed lines) was first cut through a whole sample and a structure of the YBCO material nearby its top surface (i.e. inside the a-GSs) was studied in a polarized light. We found out that the boundaries (a-a-GSBs) of two adjacent a-GSs are free of subgrains, the subgrain-free band of ≈ 1 mm thickness bears from the top surface down to the c-GS. The more the distance from a-a-GSBs, the larger becomes the polarized light contrast which follows an increase of mis-orientation angle between neighboring subgrains [6]. The spatial distribution of 211-inclusions along the a-habit presented in Figs. 2(a), (b) seems also closely related to the growth of the YBCO crystal in GSs. Both their average size d_{211} and volume fraction V_{211} dependencies have nicely symmetric, W-like shape.

Similar behavior is registered for the transition temperature T_c presented in Fig. 2(d). To obtain these data as well as distributions of critical current densities $j_c(H \parallel c)$ at different temperatures shown in Figs. 2(e), (f), the slice was diced into 11 samples (each of sizes $2.8 \times 2 \times 2.4$ mm), which magnetic properties were measured with ac-susceptometer (0.1 Oe, 20 KHz) and vibrating sample magnetometer (Oxford Instruments, VSM 3001). In fact, the plot (d) presents two temperatures where the transition starts (T_c) and ends. These are determined as the points wherein ac-susceptibility χ (normalized to unity) approaches the values -0.1 (circles) and -0.9 (squares), respectively. The open points are obtained when $H \parallel c$, the closed ones correspond to $H \parallel ab$.

The lowest-level j_c isoline at $T = 89$ K $\rightarrow T_c$ (solid black curve in Fig. 2e), i.e. the line connecting the irreversibility points H_{IL} of studied samples, confirms the W-like distribution of T_c which, according to a common opinion [7], reflects a difference in an oxygen content. Since an oxygen is

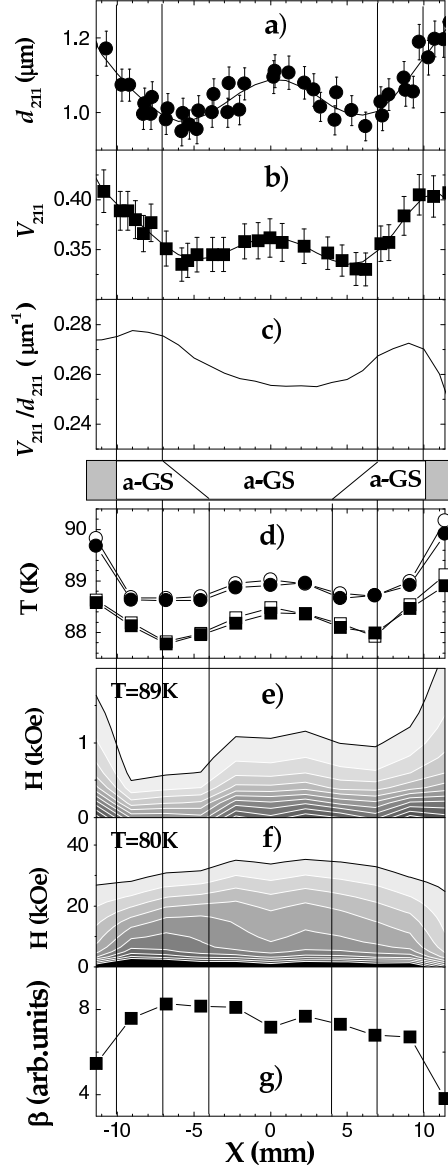


Figure 2. Variation of some structural (a)–(c) and superconducting (d)–(g) properties along the YBCO slice (see details in the text).

easy to penetrate into imperfect material containing cracks and subgrain boundaries, a quenched liquid exhibits the higher T_c . In more structurally perfect crystal T_c decreases anywhere except for the central part ($X \approx 0$) of the a-GSs. Thus, this area may be expected somewhat alike in structure to a quenched liquid.

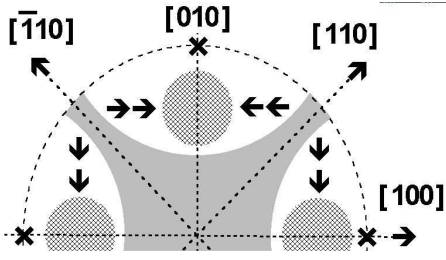


Figure 3. A feasible scenario of the YBCO crystal growth. Gray color denotes the YBCO material, shaded regions correspond to the clouds wherein 211-inclusions are pushed by secondary growth fronts (marked by double arrows).

At lower temperatures an oxygen influence on superconducting properties is no longer dominant (see Fig. 2f). The j_c vs H dependencies look more homogeneous (e.g. within the YBCO crystal $j_c(H = 0, 77\text{ K}) = 55 \pm 5\text{ kA/cm}^2$) and are well fitted by the '-1/2'-power law ($j_c \sim \beta H^{-1/2}$, where $\beta \sim V_{211}/d_{211}$), which is attributed to the 211-inclusions [7]. Besides, the spatial distribution of β (Fig. 2g) along the a-growth front looks quite similar to the value V_{211}/d_{211} which is presented in Fig. 2(c) and directly calculated from the V_{211} and d_{211} polynomial fit (solid lines). Some diversities are easy to explain: in contrast to V_{211}/d_{211} , β vs X curve corresponds to the 211-distribution *averaged* over the finite slice thickness, 2.8 mm.

3. Conclusions

In summary, one can conclude that structural and superconducting properties agree well each with other, but both are hard to explain in terms of a suggestion that a-habits are flat. At the same time, these features are readily derived from the hypothesis of concave growth fronts (see Fig. 3). Within this approach, the YBCO crystal *first* grows along the X-like 'backbone', i.e. in the $[110]$, $[1\bar{1}0]$, $[\bar{1}10]$ and $[\bar{1}\bar{1}0]$ directions (dashed arrows), whereas the *secondary* growth fronts, which respond for material inside a-GSs, are parallel to the $[100]$ and $[010]$ directions (shown by small double arrows). Since during the growth process the crystal scarcely reveals so strong pillow distortion as this shown in Fig. 3, the sec-

ondary growth fronts are expected to move much *faster* than those forming the 'backbone'. It certainly results in large mechanical stresses inside the a-GSs and, therefore, an appearance of subgrains trying to reduce these stresses. In terms of the pushing/trapping theory [8], faster motion of secondary growth fronts may also explain an increased values of d_{211} and V_{211} shown in Figs. 2(a), (b). At last, the square shape of YBCO crystals, which is well confirmed by, for instance, the remanent flux map in Fig. 1(c), means that growth process stops when the 'backbone' reaches the size of a crucible. If the growth mechanism is different from the mentioned above, the crystal could grow until *a whole* crystal fits in a crucible, i.e. in a circle.

Acknowledgements

The work was supported by the German BMBF under the project No 13N6854A3. The authors would like to thank Z.H.He and P.Diko for illuminating discussions as well as R.Müller for his continual encouragement throughout the present work. We are also indebted to P.Dittman, M.Arnz and Ch.Schmidt for technical support.

REFERENCES

1. M. Murakami, Supercond. Sci. Technol. **13** (2000) 448.
2. C. P. Bean, Rev. Mod. Phys. **36** (1964) 31.
3. C. D. Dewhurst *et al.*, Mater. Sci. Eng. B**53** (1998) 169.
4. A. B. Surzhenko *et al.*, Supercond. Sci. Technol. **14** (2001) 770.
5. D. Litzkendorf *et al.*, Mater. Sci. Eng. B**53** (1998) 75.
6. P. Diko, Supercond. Sci. Technol. **13** (2000) 1202.
7. F. Sandiumenge, B. Martinez and X. Obradors, Supercond. Sci. Technol. **10** (1997) A93.
8. C. Kim, H. G. Lee, K. B. Kim and G. W. Hong, J. Mater. Res. **10** (1995) 1605.